



ΔΗΛΩΣΗ ΕΠΙΔΟΣΕΩΝ



DoP: 0147

για fischer μπετόβιδα ULTRACUT FBS II (Εκτονούμενα αγκύρια για χρήση σε μπετόν (ελαφριάς καταπόνησης)) – EL

1. Μοναδικός κωδικός ταυτοποίησης του τύπου του προϊόντος: **DoP: 0147**
2. Προβλεπόμενη(-ες) χρήση(-εις): **Για χρήση σε ομάδα σε μη φέρουσες εφαρμογές σε ρηγματωμένο και μη ρηγματωμένο σκυρόδεμα. Για χρήση σε στηρίξεις για δευτερεύοντα δομικά στοιχεία, π.χ. ψευδοροφές, αναρτήσεις σε Η/Μ εφαρμογές, δείτε το προσάρτημα, ειδικά τα παραρτήματα B 1 - B 5**
3. Κατασκευαστής: **fischerwerke GmbH & Co. KG, Klaus-Fischer-Straße 1, 72178 Waldachtal, Γερμανία**
4. Εξουσιοδοτημένος αντιπρόσωπος: --
5. Σύστημα/συστήματα AVCP (αξιολόγηση και επαλήθευση της σταθερότητας της επίδοσης): **2+**
6. Ευρωπαϊκό έγγραφο αξιολόγησης: **EAD 330747-00-0601**
Ευρωπαϊκή τεχνική αξιολόγηση: **ETA-18/0242; 2018-10-30**
Οργανισμός τεχνικής αξιολόγησης: **DIBt**
Κοινοποιημένος(-οι) οργανισμός(-οι): **1343 – MPA Darmstadt**
7. Δηλωθείσα(-ες) επίδοση(-εις):

Ασφάλεια σε περίπτωση φωτιάς (BWR 2)

- Αντίδραση σε φωτιά : Το Αγκύριο καλύπτει τις απαιτήσεις της Κατηγορίας A 1
- Αντίσταση στη φωτιά: δείτε το παράρτημα, συγκεκριμένα τα παραρτήματα C 3

Ασφάλεια στη χρήση (BWR 4)

- χαρακτηριστική εφελκυστική αντοχή (για στατική και ημιστατική ενέργεια): δείτε το προσάρτημα, ειδικά τα παραρτήματα C 1 – C 2
- χαρακτηριστική διατμητική αντοχή (για στατική και ημιστατική ενέργεια): δείτε το προσάρτημα, ειδικά τα παραρτήματα C 1 – C 2

8. Κατάλληλη τεχνική τεκμηρίωση και/ή ειδική τεχνική τεκμηρίωση: ---

Η επίδοση του προϊόντος που ταυτοποιείται ανωτέρω είναι σύμφωνη με τη (τις) δηλωθείσα(-ες) επίδοση(-εις). Αυτή η δήλωση επιδόσεων εκδίδεται σύμφωνα με τον Κανονισμό (ΕΕ) Αρ. 305/2011 με αποκλειστική ευθύνη του κατασκευαστή που προσδιορίζεται παραπάνω.

Υπογραφή για λογαριασμό και εξ ονόματος του κατασκευαστή από:

Andreas Bucher, Dipl.-Ing.

Wolfgang Hengesbach, Dipl.-Ing., Dipl.-Wirtsch.-Ing.

Tumlingen, 2018-11-06

- Αυτή η Δήλωση Απόδοσης μεταφράστηκε σε διάφορες γλώσσες. σε περίπτωση που υπάρχει αμφιβολία για τη μετάφραση η αγγλική έκδοση θα υπερισχύει πάντα.
- Το παράρτημα περιλαμβάνει προαιρετικές και συμπληρωματικές πληροφορίες στα αγγλικά. Αυτές ξεπερνούν τις προβλεπόμενες από το νόμο (γλώσσα ουδέτερη) .

Specific Part**1 Technical description of the product**

The fischer concrete screw ULTRACUT FBS II is an anchor of size 6 mm made of hardened carbon steel. The anchor is screwed into a predrilled cylindrical drill hole. The special thread of the anchor cuts an internal thread into the member while setting. The anchorage is characterised by mechanical interlock in the special thread.

The product description is given in Annex A.

2 Specification of the intended use in accordance with the applicable EAD

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment**3.1 Safety in case of fire (BWR 2)**

Essential characteristic	Performance
Reaction to fire	Class A1
Resistance to fire	See Annex C 3

3.2 Safety in use (BWR 4)

Essential characteristic	Performance
Characteristic resistance to tension load (static and quasi-static loading)	See Annex C 1 and C 2
Characteristic resistance to shear load (static and quasi-static loading)	See Annex C 1 and C 2


4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with European Assessment Document EAD No. 330747-00-0601, the applicable European legal act is: [97/161/EC].


The system to be applied is: 2+

Product in the installed condition

Installed condition in normal weight concrete

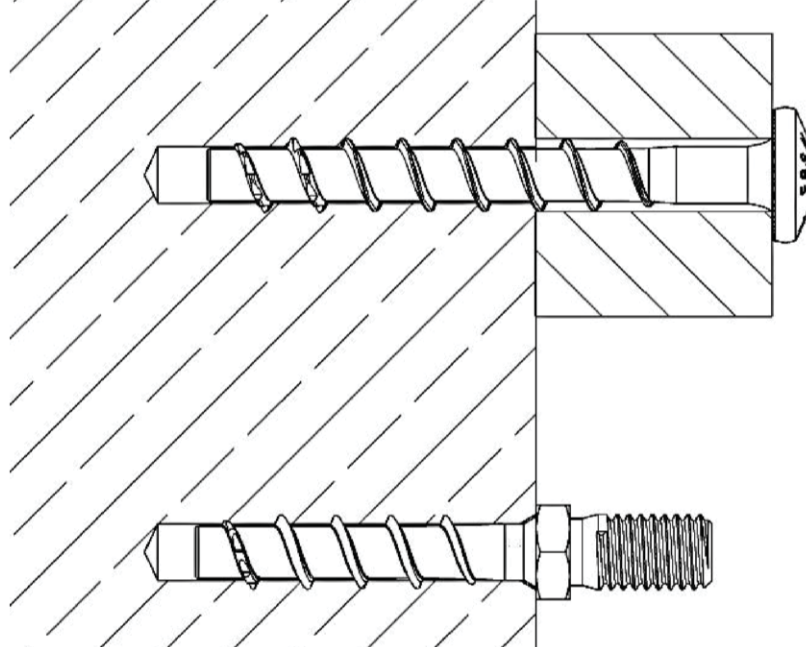

Installed condition in prestressed hollow core slabs

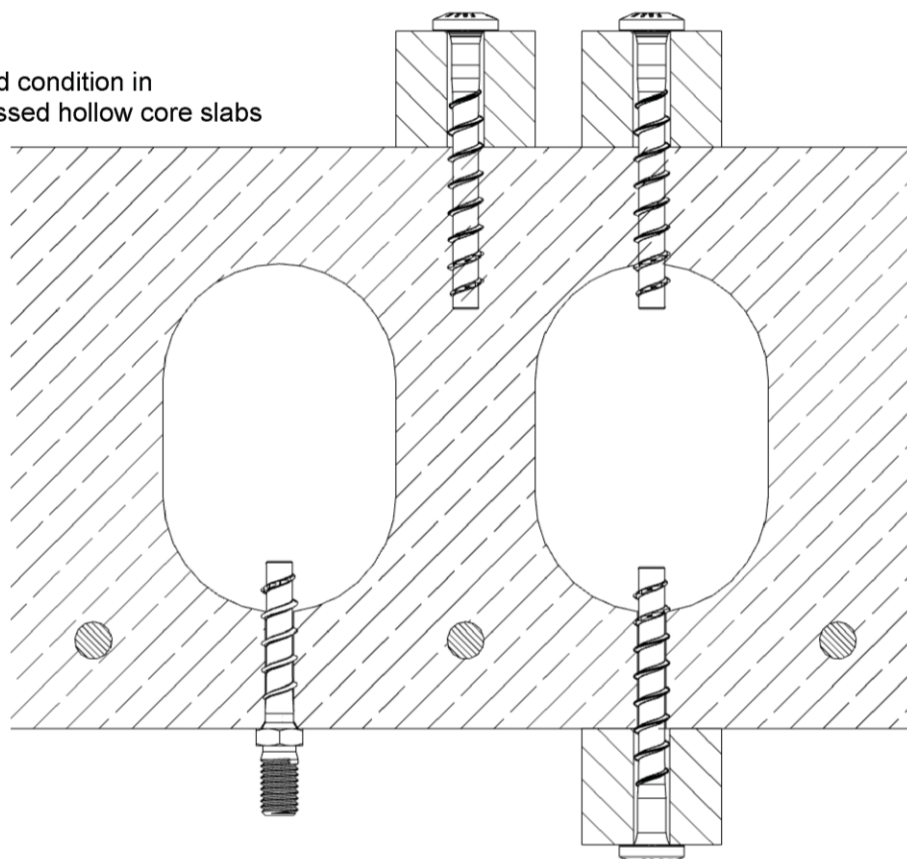









fischer concrete screw ULTRACUT FBS II

Product description

Product in the installed condition

Annex A 1

Table A2.1: Screw types**FBS II 6**

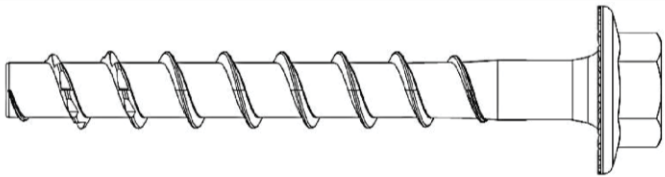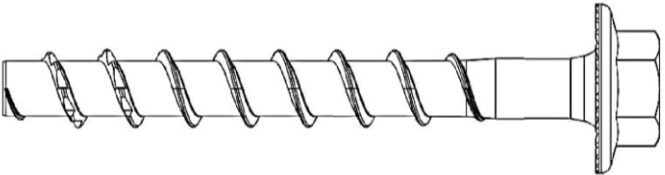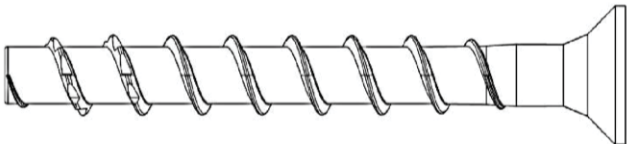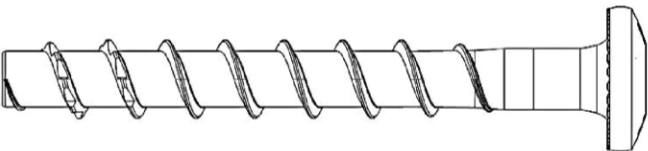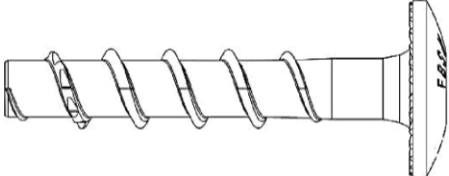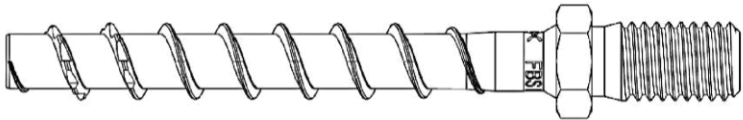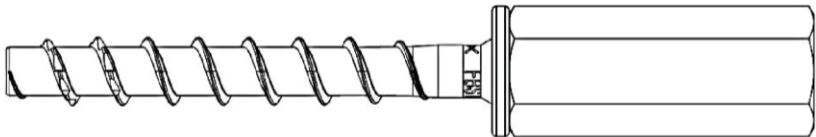
Hexagon head with formed washer (US)		
Hexagon head with formed washer and TX-drive (US TX)		
Countersunk head (SK)		
Pan head (P)		
Large pan head (LP)		
Hexagon head and connection thread M8 or M10 (M)		
Internal thread M8 / M10 combined (M8 / M10 I)		

fischer concrete screw ULTRACUT FBS II

Product description
 Screw types
Annex A 2


Table A3.1: Geometry and material

FBS II 6			All head shapes
Thread outer diameter	d_a	[mm]	7,75
Core diameter	d_k		5,65
Shaft diameter	d_s		6,0
Material	[-]	Hardened carbon steel; $A_{5\%} \geq 8\%$	
Coating		galvanized	

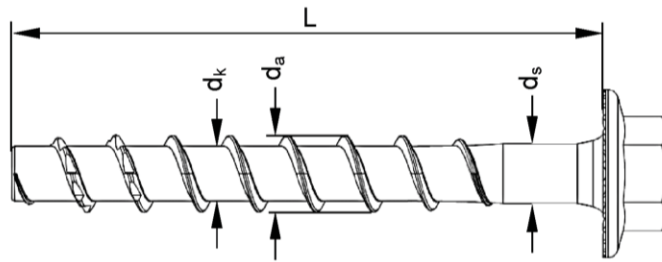
**Head marking at US, US TX, SK, P, LP**

FBS II: Product identification

XXX: Screw length L



6: Screw size

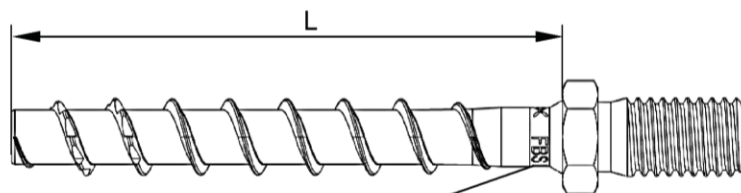Marking at M8, M10, M8 / M10 IHead marking:
XX: Screw length LRotary marking:
FBS II: Product identification
6: Screw size

fischer concrete screw ULTRACUT FBS II

Product description
Geometry and marking**Annex A 3**

Specification of intended use:

Anchorage subject to:

- Static and quasi static loads: all types and embedment depths
- Used in concrete for redundant non-structural systems
- Used for fire: only for concrete C20/25 to C50/60 (does not apply for prestressed hollow core slabs)

Base materials:

- Compacted reinforced or unreinforced normal weight concrete without fibres according to EN 206:2013
- Strength classes C20/25 to C50/60 according to EN 206:2013
- Uncracked or cracked concrete
- Prestressed hollow core slabs, where the cavity width does not exceed 4.2 times the web width ($b_H \leq 4,2 \times b_{SI}$) with strength classes C30/37 to C50/60

Use conditions (Environmental conditions):

- Structures subjected to dry internal conditions

Design:

- Anchorages are to be designed under the responsibility of an engineer experienced in anchorages and concrete work
- Verifiable calculation notes and drawings are to be prepared taking account of the loads to be anchored. The position of the screw is indicated on the design drawings (e.g. position of the screw relative to reinforcement or to supports, etc.)
- Design of fastenings according to FprEN 1992-4: 2016 and EOTA Technical Report TR 055

Installation:

- Hammer drilling or hollow drilling
- Screw installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters on site
- In case of aborted hole: New hole must be drilled at a minimum distance of twice the depth of the aborted hole or closer, if the hole is filled with a high strength mortar and only if the hole is not in the direction of the oblique tensile or shear load
- Adjustability according to Annex B3
- Cleaning of drill hole is not necessary when using a hollow drill or:
 - If drilling vertically upwards
 - If drilling vertically downwards and the drill hole depth has been increased. It is recommended to increase the drill depth with additional $3 d_0$
- After correct installation further turning of the screw head shall not be possible
- The head of the screw must be fully engaged on the fixture and show no signs of damage
- In prestressed hollow core slabs the screw may be installed from all directions, if the web thickness and the spacing to the tensioning strands according to table B3.1 are observed (also in the area of solid material)

fischer concrete screw ULTRACUT FBS II

Intended use
Specification

Annex B 1


Table B2.1: Installation parameters – drilling bore hole and setting tools

FBS II 6			All head shapes	
Nominal embedment depth	h_{nom}	[mm]	$25 \leq h_{nom} < 35$	$35 \leq h_{nom} \leq 55$
Nominal drill hole diameter	d_0		6	
Cutting diameter of drill bits	$d_{cut} \leq$		6,4	
Clearance hole diameter	$d_f \leq$		8	
Drill hole depth			$h_{nom} + 5$	$h_{nom} + 10^{1)}$
Drill hole depth (with adjustable setting)	$h_1 \geq$		$h_{nom} + 15$	$h_{nom} + 20$
Torque impact screw driver	$T_{imp,max}$	[Nm]	80	450
Maximum installation torque with hexagon nut on head shapes M8, M10 and M8/M10 I	T_{max}		5	10

¹⁾ Value can be reduced to $h_{nom} + 5$ for installation vertically upwards

Table B2.2: Installation parameters – drive and fixture

FBS II 6			US	US TX	SK	P	LP	M8	M10	M8/M10 I
Wrench size	SW	[mm]	10		-			10	13	
TX size	TX	[-]	-	30				-		
Head diameter	d _h	[mm]	17		13,5	14,4	17,5			
Thickness of fixture	t _{fix} ≤		L - h _{nom}							
Length of screw	L _{min} =		25							
	L _{max} =	325						55		

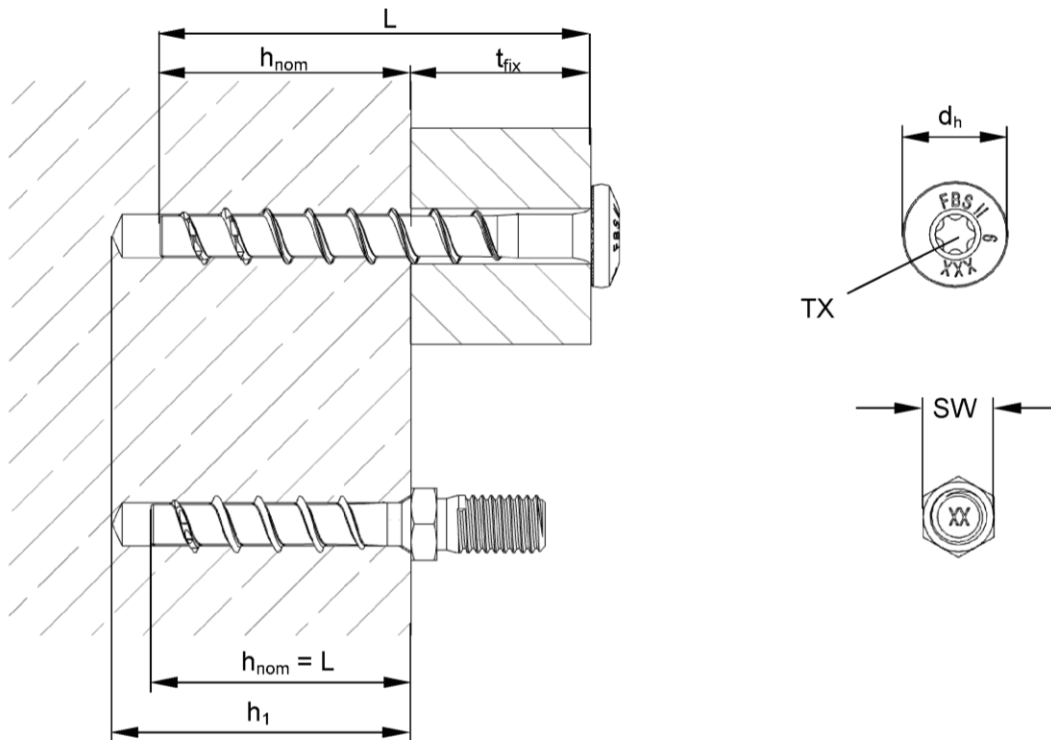

fischer concrete screw ULTRACUT FBS II

Intended use
Installation parameters

Annex B 2


Table B3.1: Installation parameters – Additional information for prestressed hollow core slabs

FBS II 6				
Distance to the tensioning strands	$a_p \geq$	[mm]	50	
Thickness of the slab web	$d_b \geq$		25	
Minimum thickness of fixture	$t_{fix} \geq$		$L - d_b^{1)} - 30 \text{ mm}$	
Torque impact screw driver	$T_{imp,max}$	[Nm]	80 (450 ²⁾)	


1) If d_b is not known, then set $d_b = 25 \text{ mm}$

2) Parent value applies if all the following conditions are met:

- $d_b \geq 35 \text{ mm}$
- $h_{nom} \geq 35 \text{ mm}$

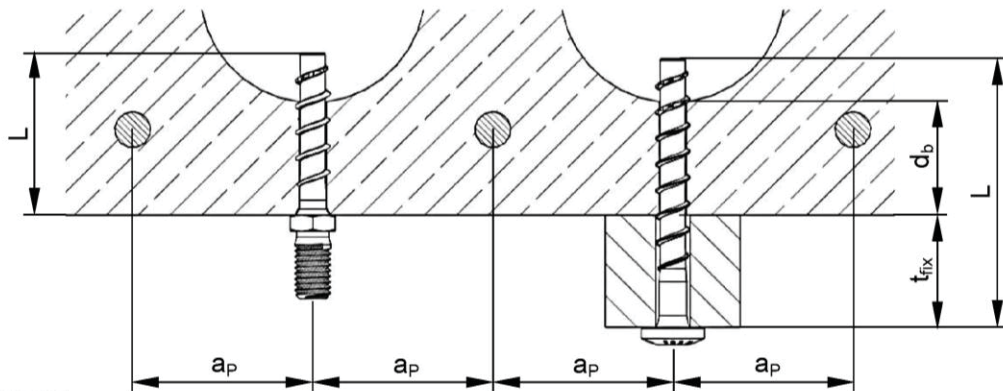

Adjustment

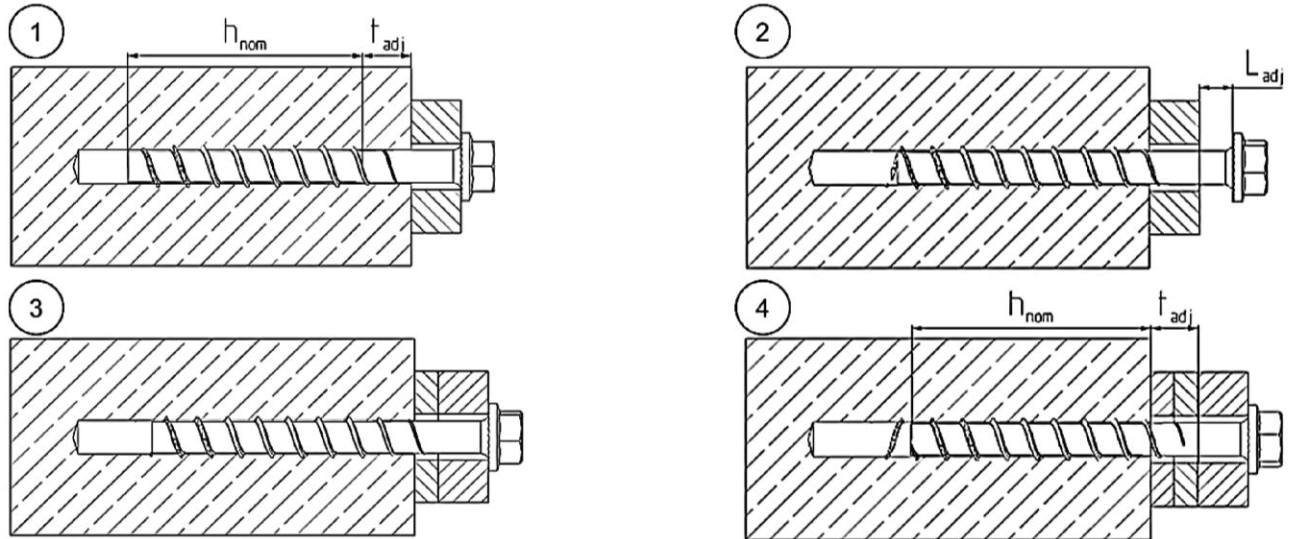

It is permissible to untighten the screw up to two times for adjustment purposes.

Therefore the screw may be untightened to a maximum of $L_{adj} = 20 \text{ mm}$ to the surface of the initial fixture.

The total permissible thickness of shims added during the adjustment process is $t_{adj} = 10 \text{ mm}$.

fischer concrete screw ULTRACUT FBS II

Intended use

Prestressed hollow core slabs and adjustment

Annex B 3

Table B4.1: Minimum thickness of concrete members, minimum spacing and edge distance**FBS II 6**

Minimum thickness of concrete member	$h_{\min}$		$\max.(80; h_1^{1}) + 30)$
Minimum spacing	$s_{\min}$		35
Minimum edge distance	$c_{\min}$		

¹⁾ Drill hole depth according to table B2.1

Table B4.2: Minimum spacing and edge distance for prestressed hollow core slabs**FBS II 6**

Minimum spacing	$s_{\min}$	[mm]	100
Minimum edge distance	$c_{\min}$		
Minimum distance between anchor groups	$a_{\min}$		

fischer concrete screw ULTRACUT FBS II

Intended use

Minimum thickness of members, minimum spacing and edge distance

Annex B 4

Installation instruction**Installation of fischer concrete screw ULTRACUT FBS II 6**










 		For installation in prestressed hollow core slabs: Determine and mark the position of the tensioning strands, e.g. with a suitable scanner. Keep distances to the tensioning strands according to table B3.1.
		Drill the hole using hammer drill or hollow drill. Drill hole diameter d_0 and drill hole depth h_1 according to table B2.1
a) 	b) 	Option a): Clean the drill hole Option b): Cleaning of drill hole is not necessary when using a hollow drill or: - If drilling vertically upwards or - If drilling vertically downwards and the drill hole depth has been increased. It is recommended to increase the drill hole depth additional 3 times d_0 .
		Installation with any torque impact screw driver up to the maximum mentioned torque moment ($T_{\text{imp,max}}$ according table B2.1). Alternatively, all other tools without an indicated torque moment are allowed (e.g. ratchet spanner). The indicated torque moments for impact screw driver are therefore not decisive.
		After installation a further turning of the screw must not be possible. The head of the screw must be in contact with the fixture and is not damaged.
1. 	2. 	OPTIONAL: It is permissible to adjust the screw twice. Therefore the screw may be untightened to a maximum of $L_{\text{adj}} = 20 \text{ mm}$ off the surface of the initial fixture. The total permissible thickness of shims added during the adjustment process is $t_{\text{adj}} = 10 \text{ mm}$.
3. 		
fischer concrete screw ULTRACUT FBS II		Annex B 5
Intended use Installation instruction		

Table C1.1: Characteristic values for static and quasi-static action

FBS II 6										
Nominal embedment depth		h_{nom}	[mm]	25	30	35	40	45	50	55
Steel failure for tension load and shear load										
Characteristic resistance		$N_{Rk,s}$	[kN]	21						
Partial factor		γ_{Ms}	[-]	1,4						
Characteristic resistance		$V_{Rk,s}$	[kN]	4,8		9,0				13,3
Partial factor		γ_{Ms}	[-]	1,5						
Factor for ductility		k_7		1,0						
Characteristic bending resistance		$M^0_{Rk,s}$	[Nm]	17,1						
Pullout failure										
Characteristic resistance in concrete C20/25	uncracked	$N_{Rk,p}$	[kN]	3,0	5,0	6,5	8,0	10,0	12,0	13,5
	cracked			1,5	2,5	3,5	5,0	6,0	7,5	8,5
Increasing factors concrete	C25/30	ψ_c	[-]	1,12						
	C30/37			1,22						
	C35/45			1,32						
	C40/50			1,41						
	C45/55			1,50						
	C50/60			1,58						
Installation factor		γ_{inst}		1,0						
Concrete cone failure and splitting failure; concrete pryout failure										
Effective embedment depth		h_{ef}	[mm]	19	23	27	32	36	40	44
Factor for uncracked concrete		$k_{ucr,N}$	[-]	11,0						
Factor for cracked concrete		$k_{cr,N}$		7,7						
Characteristic edge distance		$c_{cr,N}$	[mm]	$1,5 h_{ef}$						
Characteristic spacing		$s_{cr,N}$		$3 h_{ef}$						
Charakt. resistance for splitting		$N^0_{Rk,sp}$	[kN]	$N_{Rk,c}$						
Charact. edge distance for splitting		$c_{cr,sp}$	[mm]	$2 \times h_{ef}$			$1,5 \times h_{ef}$			
Charakt. spacing for splitting		$s_{cr,sp}$		$4 \times h_{ef}$			$3 \times h_{ef}$			
Factor for pryout failure		k_8	[-]	1,3		2,0				
Installation factor		γ_{inst}		1,0						
Concrete edge failure										
Effective length in concrete		l_f	[mm]	25	30	35	40	45	50	55
Nominal diameter of screw		d_{nom}		6						
Adjustment										
Maximum thickness of shims		t_{adj}	[mm]	10						
Max. number of adjustments		n_a	[-]	2						
fischer concrete screw ULTRACUT FBS II									Annex C 1	
Performances Characteristic values										

Table C2.1:	Characteristic values for static and quasi-static action in prestressed hollow core slabs
--------------------	---

FBS II 6

Nominal embedment depth		h_{nom}	[mm]	25	30	35	40	45	50	55	
Steel failure for tension load and shear load											
Characteristic resistance		$N_{RK,s}$	[kN]	21							
Partial factor		γ_{Ms}	[-]	1,4							
Characteristic resistance		$V_{RK,s}$	[kN]	4,8		9,0				13,3	
Partial factor		γ_{Ms}	[-]	1,5							
Factor for ductility		k_7		1,0							
Characteristic bending resistance		$M^0_{RK,s}$	[Nm]	17,1							
Pullout failure, Concrete cone failure, Concrete edge failure, Concrete pryout failure for all load directions											
Characteristic resistance in C30/37 for thickness of the slab web	$d_b \geq 25 \text{ mm}$	$F_{RK,p}$	[kN]	0,5	1,0						
	$d_b \geq 30 \text{ mm}$			3,5							
	$d_b \geq 35 \text{ mm}$			3,5	4,0	4,5	5,0	5,5	6,0	6,5	
	$d_b \geq 40 \text{ mm}$				5,0	5,5	6,0	7,0	7,5	8,0	
	$d_b \geq 50 \text{ mm}$				5,5	7,0	8,0	9,5	11,0	12,0	
Increasing factor concrete	C35/45	ψ_c	[-]	1,08							
	C40/50			1,15							
	C45/55			1,22							
	C50/60			1,29							
Installation factor		γ_{inst}	[-]	1,0							

fischer concrete screw ULTRACUT FBS II

Performances

Performance

Characteristic values in prestressed hollow core slabs

Annex C 2

Table C3.1: Characteristic values for resistance to fire ¹⁾									
FBS II 6									
Nominal embedment depth	h_{nom}	[mm]	25	30	35	40	45	50	55
Steel failure for tension load and shear load ($F_{Rk,s,fi} = N_{Rk,s,fi} = V_{Rk,s,fi}$)									
Characteristic resistance for all head shapes	$F_{Rk,s,fi}$	R30	[kN]	1,00					
		R60		0,60					
		R90		0,50					
		R120		0,40					
Characteristic bending resistance for all head shapes	$M^0_{Rk,s,fi}$	R30	[Nm]	0,80					
		R60		0,50					
		R90		0,40					
		R120		0,35					
Edge distance									
R30 to R120	$c_{cr,fi}$	[mm]	2 h_{ef}						
In case of fire attack from more than one side, the minimum edge distance shall be ≥ 300 mm									
Spacing									
R30 to R120	$s_{cr,fi}$	[mm]	2 $c_{cr,fi}$						
¹⁾ The embedment depth has to be increased for wet concrete by at least 30 mm compared to the given value.									
fischer concrete screw ULTRACUT FBS II								Annex C 3	
Performances Characteristic values for resistance to fire									