

DECLARATION OF PERFORMANCE

DoP 0283

for fischer injection system FIS EB (Bonded fastener for use in concrete)

EN

1. Unique identification code of the product-type: **DoP 0283**
2. Intended use/es: **Post-installed fastening for use in cracked or uncracked concrete see appendix, especially annexes B1 - B9.**
3. Manufacturer: **fischerwerke GmbH & Co. KG, Otto-Hahn-Straße 15, 79211 Denzlingen, Germany**
4. Authorised representative: **–**
5. System/s of AVCP: **1**
6. European Assessment Document: **ETAG 001, Part 5, April 2013, used as EAD**
 European Technical Assessment: **ETA-15/0440; 2017-12-13**
 Technical Assessment Body: **DIBt- Deutsches Institut für Bautechnik**
 Notified body/ies: **2873 TU Darmstadt**
7. Declared performance/s:
Mechanical resistance and stability (BWR 1)
Characteristic resistance to tension load (static and quasi-static loading):
 Resistance to steel failure: Annexes C1, C2
 Resistance to combined pull- out and concrete cone failure: Annexes C4, C5

 Resistance to concrete cone failure: Annex C3
 Edge distance to prevent splitting under load: Annex C3
 Robustness: Annexes C3-C5, C9, C10
 Maximum installation torque: Annex B3
 Minimum edge distance and spacing: Annexes B3, B4

Characteristic resistance to shear load (static and quasi-static loading):
 Resistance to steel failure: Annexes C1, C2
 Resistance to pry-out failure: Annex C3
 Resistance to concrete edge failure: Annex C3
 (k₇=k₂)
 (k₈=k₃)

Displacements under short-term and long-term loading:
 Displacements under short-term and long-term loading: Annexes C6

Characteristic resistance and displacements for seismic performance categories C1 and C2:
 Resistance to tension load, displacements, category C1: Annexes C7-C9
 Resistance to tension load, displacements, category C2: Annexes C7, C10
 Resistance to shear load, displacements, category C1: Annexes C7, C8
 Resistance to shear load, displacements, category C2: Annex C7
 Factor for annular gap: NPD

Hygiene, health and the environment (BWR 3)
 Content, emission and/or release of dangerous substances: NPD
8. Appropriate Technical Documentation and/or **–**
Specific Technical Documentation:

The performance of the product identified above is in conformity with the set of declared performance/s. This declaration of performance is issued, in accordance with Regulation (EU) No 305/2011, under the sole responsibility of the manufacturer identified above.

Signed for and on behalf of the manufacturer by:




Dr.-Ing. Oliver Geibig, Managing Director Business Units & Engineering
 Tümlingen, 2021-01-19

Jürgen Grün, Managing Director Chemistry & Quality

This DoP has been prepared in different languages. In case there is a dispute on the interpretation the English version shall always prevail.

The Appendix includes voluntary and complementary information in English language exceeding the (language-neutrally specified) legal requirements.

Specific Part

1 Technical description of the product

The fischer injection system FIS EB is a bonded anchor consisting of a cartridge with injection mortar fischer FIS EB and a steel element.

The steel element is placed into a drilled hole filled with injection mortar and is anchored via the bond between metal part, injection mortar and concrete.

The product description is given in Annex A.

2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Characteristic values under static and quasi-static action, Displacements	See Annex C 1 to C 6
Characteristic values for seismic performance categories C1 and C2 5, Displacements	See Annex C 7 to C 10

3.2 Safety in case of fire (BWR 2)

Essential characteristic	Performance
Reaction to fire	Anchorage satisfy requirements for Class A1
Resistance to fire	No performance assessed

3.3 Hygiene, health and the environment (BWR 3)

Regarding dangerous substances there may be requirements (e.g. transposed European legislation and national laws, regulations and administrative provisions) applicable to the products falling within the scope of this European Technical Assessment. In order to meet the provisions of Regulation (EU) No 305/2011, these requirements need also to be complied with, when and where they apply.

3.4 Safety in use (BWR 4)

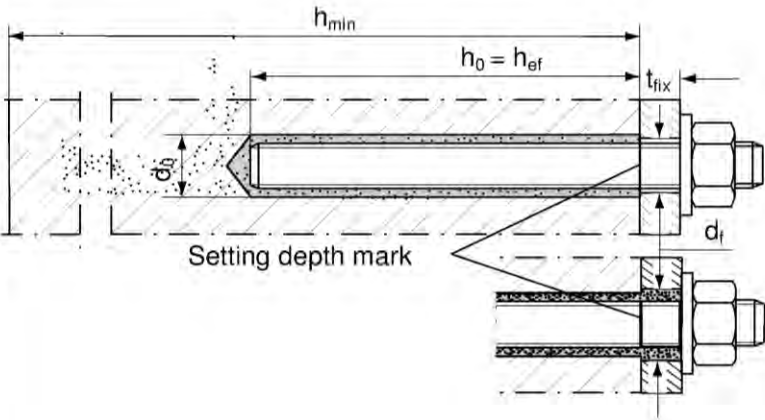
The essential characteristics regarding Safety in use are included under the Basic Works Requirement Mechanical resistance and stability.

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with guideline for European technical approval ETAG 001, April 2013 used as European Assessment Document (EAD) according to Article 66 Paragraph 3 of Regulation (EU) No 305/2011 the applicable European legal act is: [96/582/EC].


The system to be applied is: 1

Installation conditions



Anchor rod
Pre-positioned anchor

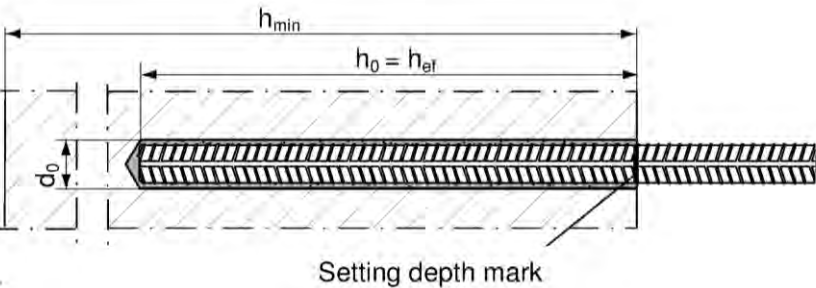Anchor rod
Push through anchor
(annular gap filled with mortar)



Reinforcing bar


Cartridge sizes (390 ml, 585 ml, 1100 ml, 1500 ml)

Imprint: fischer FIS EB, processing notes, shelf-life, piston travel scale, curing times and processing times (depending on temperature), hazard code, size, volume


Sealing cap




1




Injection-adapter



Static mixer FIS MR, FIS MR Plus or FIS UMR




Extension tube



Anchor rod

Size: M8, M10, M12, M14, M16, M20, M22, M24, M27, M30



2

Washer



3


Hexagon nut



4

Reinforcing bar

Nominal diameter of the bar: $\phi 8$, $\phi 10$, $\phi 12$, $\phi 14$, $\phi 16$, $\phi 18$, $\phi 20$, $\phi 22$, $\phi 24$, $\phi 25$, $\phi 26$, $\phi 28$, $\phi 30$, $\phi 32$, $\phi 34$, $\phi 36$, $\phi 40$



5

fischer injection system FIS EB

Product description

Cartridges / Static mixer / Steel elements

Annex A 2

Appendix 4 / 24

Table A1: Materials

Part	Designation	Material	
1	Mortar cartridge	Mortar, hardener, filler	
	Steel grade	Steel, zinc plated	Stainless steel A4
2	Anchor rod	Property class 5.8 or 8.8; EN ISO 898-1:2013 zinc plated $\geq 5 \mu\text{m}$, EN ISO 4042:1999 A2K or hot-dip galvanized $\geq 40 \mu\text{m}$ EN ISO 10684:2004 $f_{uk} \leq 1000 \text{ N/mm}^2$ $A_5 > 12 \%$ fracture elongation	Property class 50, 70 or 80 EN ISO 3506-1:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362; 1.4062, 1.4662, 1.4462 EN 10088-1:2014 $f_{uk} \leq 1000 \text{ N/mm}^2$ $A_5 > 12 \%$ fracture elongation ¹⁾
		fracture elongation $A_5 > 8 \%$ for applications without requirements for seismic performance category C2	
3	Washer ISO 7089:2000	zinc plated $\geq 5 \mu\text{m}$, EN ISO 4042:1999 A2K or hot-dip galvanized $\geq 40 \mu\text{m}$ EN ISO 10684:2004	1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362 EN 10088-1:2014
4	Hexagon nut	Property class 5 or 8; EN ISO 898-2:2012 zinc plated $\geq 5 \mu\text{m}$, ISO 4042:1999 A2K or hot-dip galvanized $\geq 40 \mu\text{m}$ EN ISO 10684:2004	Property class 50, 70 or 80 EN ISO 3506-1:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362 EN 10088-1:2014
7	Reinforcing bar EN 1992-1-1:2004 and AC:2010, Annex C	Bars and de-coiled rods, class B or C with f_{yk} and k according to NDP or NCL of EN 1992-1-1:2004+AC:2010 $f_{uk} = f_{tk} = k \cdot f_{yk}$	






fischer injection system FIS EB

Product description
 Materials
Annex A 3

Appendix 5 / 24

Specifications of intended use (part 1)

Table B1: Overview use and performance categories

Anchorages subject to		FIS EB with ...			
		Anchor rod		Reinforcing bar	
					
Hammer drilling with standard drill bit 		all sizes			
Hammer drilling with hollow drill bit (Heller "Duster Expert" or Hilti "TE-CD, TE-YD") 		Nominal drill bit diameter (d ₀) 12 mm to 35 mm			
Diamond drilling 		all sizes			
Static and quasi static load, in	uncracked concrete	all sizes	Tables: C1, C3, C4, C6	all sizes	Tables: C2, C3, C5, C7
	cracked concrete				
Seismic performance category (only hammer drilling with Standard / hollow drill bits)	C1	M10 to M30	Tables: C8, C10, C11	φ10 to φ32	Tables: C9, C10, C12
	C2	M12, M16, M20, M24	Tables: C8, C10, C13	---	---
Use category	dry or wet concrete	all sizes			
	flooded hole	all sizes			
Installation temperature		+5 °C to +40 °C			
In-service temperature		-40 °C to +72 °C (max. long term temperature +50 °C and max. short term temperature +72 °C)			

fischer injection system FIS EB

Intended use
Specifications (part 1)

Annex B 1

Appendix 6 / 24

Specifications of intended use (part 2)

Base materials:

- Reinforced or unreinforced normal weight concrete Strength classes C20/25 to C50/60 according to EN 206-1:2000

Use conditions (Environmental conditions):

- Structures subject to dry internal conditions (zinc coated steel, stainless steel)
- Structures subject to external atmospheric exposure (including industrial and marine environment) and to permanently damp internal condition, if no particular aggressive conditions exist (stainless steel)

Note: Particular aggressive conditions are e.g. permanent, alternating immersion in seawater or the splash zone of seawater, chloride atmosphere of indoor swimming pools or atmosphere with extreme chemical pollution (e.g. in desulphurization plants or road tunnels where de-icing materials are used)

Design:

- Anchorages have to be designed by a responsible engineer with experience in anchorages and concrete work
- Verifiable calculation notes and drawings are to be prepared taking account of the loads to be anchored. The position of the anchor is indicated on the design drawings (e.g. position of the anchor relative to reinforcement or to supports, etc.)
- Anchorages under static or quasi-static actions are designed in accordance with EOTA Technical Report TR 029 "Design of bonded anchors" Edition September 2010 or CEN/TS 1992-4:2009
- Anchorages under seismic actions (cracked concrete) have to be designed in accordance with:
 - EOTA Technical Report TR 045 "Design of Metal Anchors under Seismic Action", Edition February 2013
 - Anchorages shall be positioned outside of critical regions (e.g. plastic hinges) of the concrete structure
 - Fastenings in stand-off installation or with a grout layer under seismic action are not allowed

Installation:

- Anchor installation is to be carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site
- In case of aborted hole: The hole shall be filled with mortar
- Anchorage depth should be marked and adhered to on installation
- Overhead installation is allowed

fischer injection system FIS EB

Intended use
Specifications (part 2)

Annex B 2

Appendix 7 / 24


Table B2: Installation parameters for anchor rods

Size		M8	M10	M12	M14	M16	M20	M22	M24	M27	M30
Width across flats	SW	13	17	19	22	24	30	32	36	41	46
Nominal drill bit diameter	d_0	12	14	14	16	18	24	25	28	30	35
Drill hole depth	h_0	$h_0 = h_{ef}$									
Effective anchorage depth	$h_{ef,min}$	60	60	70	75	80	90	93	96	108	120
	$h_{ef,max}$	160	200	240	280	320	400	440	480	540	600
Minimum spacing and minimum edge distance	$s_{min} = c_{min}$	40	45	55	60	65	85	95	105	120	140
Diameter of clearance hole in the fixture ¹⁾	pre-positioned anchorage d_f	9	12	14	16	18	22	24	26	30	33
	push through anchorage d_f	14	16	16	18	20	26	28	30	33	40
Minimum thickness of concrete member	h_{min}	$h_{ef} + 30$ (≥ 100)		$h_{ef} + 2d_0$							
Maximum installation torque	$T_{inst,max}$ [Nm]	10	20	40	50	60	120	135	150	200	300

¹⁾ For larger clearance holes in the fixture see TR 029, 4.2.2.1 or CEN/TS 1992-4-1:2009, 5.2.3.1

Anchor rod:

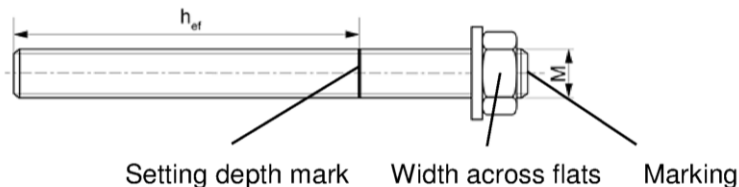**fischer
FIS A**



**fischer
RG M**



Marking (on random place) fischer anchor rod FIS A or RG M:

Property class 8.8: •

Stainless steel A4, property class 50: ••

Or colour coding according to DIN 976-1

Commercial standard threaded rods, washers and hexagon nuts may also be used if the following requirements are fulfilled:

- Materials, dimensions and mechanical properties according Annex A 3, Table A1
- Inspection certificate 3.1 according to EN 10204:2004, the documents have to be stored
- Setting depth is marked

fischer injection system FIS EB

Intended use

Installation parameters anchor rods

Annex B 3

Appendix 8 / 24


Table B3: Installation parameters for reinforcing bars

Nominal diameter of the bar ϕ		8 ¹⁾		10 ¹⁾		12 ¹⁾		14	16	18	20	22	24
Nominal drill bit diameter d_0	[mm]	10	12	12	14	14	16	18	20	25	25	30	30
Drill hole depth h_0		$h_0 = h_{ef}$											
Effective anchorage depth $\frac{h_{ef,min}}{h_{ef,max}}$		60	60	70	75	80	85	90	94	98			
		160	200	240	280	320	360	400	440	480			
Minimum spacing and minimum edge distance $\frac{s_{min}}{c_{min}}$		40	45	55	60	65	75	85	95	105			
Minimum thickness of concrete member h_{min}		$h_{ef} + 30$ (≥ 100)						$h_{ef} + 2d_0$					

Nominal diameter of the bar ϕ		25	26	28	30	32	34	36	40	---
Nominal drill bit diameter d_0	[mm]	30	35	35	40	40	40	45	55	---
Drill hole depth h_0		$h_0 = h_{ef}$								
Effective anchorage depth $\frac{h_{ef,min}}{h_{ef,max}}$		100	104	112	120	128	136	144	160	---
		500	520	560	600	640	680	720	800	---
Minimum spacing and minimum edge distance $\frac{s_{min}}{c_{min}}$		110	120	130	140	160	170	180	200	---
Minimum thickness of concrete member h_{min}		$h_{ef} + 2d_0$								

¹⁾ Both drill bit diameters can be used

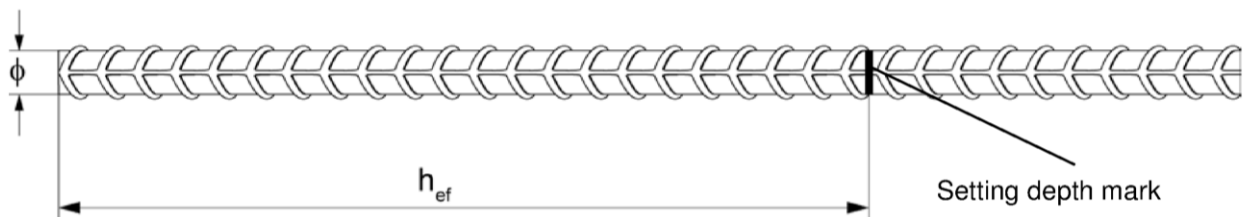Reinforcing bar



- The minimum value of related rib area $f_{R,min}$ must fulfil the requirements of EN 1992-1-1:2004+AC:2010
- The rib height must be within the range: $0,05 \cdot \phi \leq h_{rib} \leq 0,07 \cdot \phi$
(ϕ = Nominal diameter of the bar , h_{rib} = rib height)

fischer injection system FIS EB

Intended use
Installation parameters reinforcing bars

Annex B 4

Appendix 9 / 24

Table B4: Parameters of cleaning brush (steel brush) BS Ø

Drill bit diameter	d_0	[mm]	12	14	16	18	20	24	25	28	30	32	35	40	45	55
Steel brush diameter	d_b		14	16	20		25	26	27	30	40			42	47	58



Table B5: Maximum processing time of the mortar and minimum curing time
 (During the curing time of the mortar the concrete temperature may not fall below the listed minimum temperature)

System temperature [°C]	Maximum processing time t_{work} [minutes]	Minimum curing time ¹⁾ t_{cure} [hours]
+5 to +10	120	45
> +10 to +20	30	22
> +20 to +30	14	12
> +30 to +40	7	6

¹⁾ In wet concrete or flooded holes the curing times must be doubled

fischer injection system FIS EB

Intended use

Cleaning tools

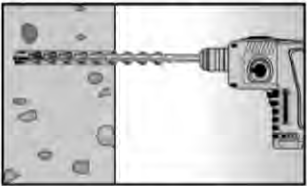
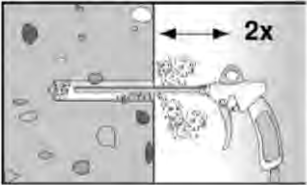

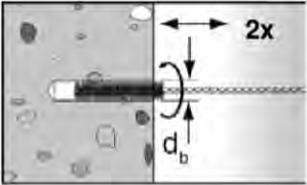
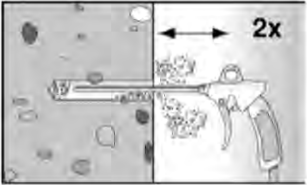

Processing times and curing times

Annex B 5

Appendix 10 / 24


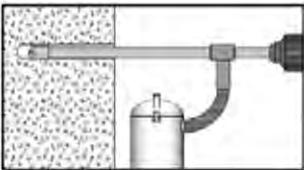
Installation instructions part 1

Drilling and cleaning the hole (hammer drilling with standard drill bit)

1		Drill the hole. Drill hole diameter d_0 and drill hole depth h_0 see Tables B2, B3	
2		Blow out the drill hole twice, with oil-free compressed air ($p \geq 6$ bar)	
3		Brush the drill hole twice. For drill hole diameter ≥ 30 mm use a power drill. For deep holes use an extension. Corresponding brushes see Table B4	
4		Blow out the drill hole twice, with oil-free compressed air ($p \geq 6$ bar)	

Go to step 6

Drilling and cleaning the hole (hammer drilling with hollow drill bit)

1		Check a suitable hollow drill (see Table B1) for correct operation of the dust extraction	
2		Use a suitable dust extraction system, e.g. Bosch GAS 35 M AFC or a comparable dust extraction system with equivalent performance data Drill the hole with hollow drill bit. The dust extraction system has to extract the drill dust nonstop during the drilling process. Diameter of drill hole d_0 and drill hole depth h_0 see Tables B2, B3	

Go to step 6

fischer injection system FIS EB

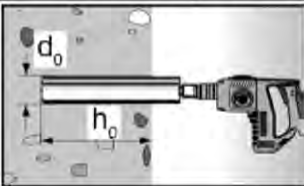
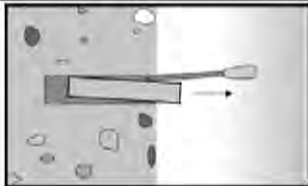
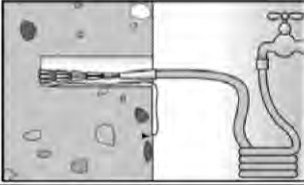
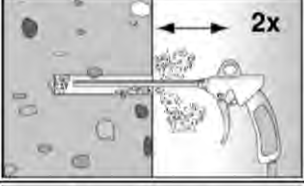
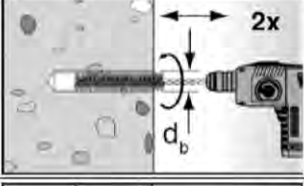
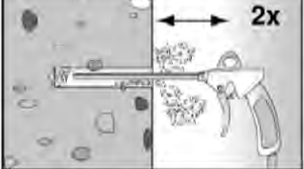
Intended use
Installation instructions part 1

Annex B 6






Appendix 11 / 24

Installation instructions part 2

Drilling and cleaning the hole (wet drilling with diamond drill bit)

1		Drill the hole. Drill hole diameter d_0 and drill hole depth h_0 see Tables B2, B3		Break the drill core and draw it out
2		Flush the drill hole with clean water until it flows clear		
3		Blow out the drill hole twice, using oil-free compressed air ($p > 6$ bar)		
4		Brush the drill hole twice using a power drill. Corresponding brushes see Table B4		
5		Blow out the drill hole twice, using oil-free compressed air ($p > 6$ bar)		

Preparing the cartridge

6		Remove the sealing cap Screw on the static mixer (the spiral in the static mixer must be clearly visible)		
7			Place the cartridge into the dispenser	
8			Extrude approximately 10 cm of material out until the resin is evenly grey in colour. Do not use mortar that is not uniformly grey	

fischer injection system FIS EB

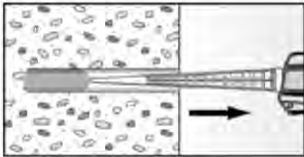
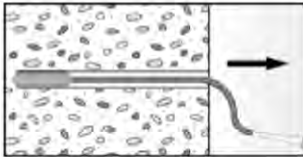
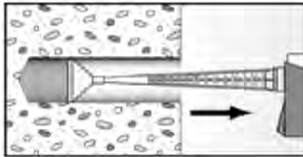
Intended use
Installation instructions part 2

Annex B 7

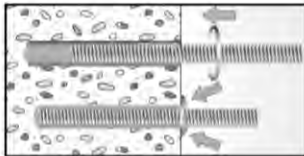

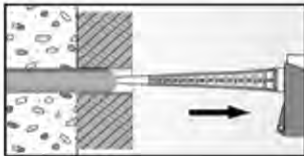

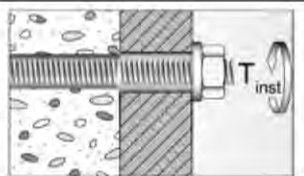
Appendix 12 / 24

Installation instructions part 3

Injection of the mortar

9	 <p>Fill approximately 2/3 of the drill hole with mortar. Always begin from the bottom of the hole and avoid bubbles</p>	 <p>For drill hole depth ≥ 150 mm use an extension tube</p>	 <p>For overhead installation, deep holes $h_0 > 250$ mm or drill hole diameter $d_0 \geq 40$ mm use an injection-adapter</p>
---	---	--	---

Installation of anchor rods

10		<p>Only use clean and oil-free anchor elements. Mark the setting depth of the anchor. Press the threaded rod down to the bottom of the hole, turning it slightly while doing so. After inserting the anchor element, excess mortar must be emerged around the anchor element. If not, pull out the anchor element immediately and reinject mortar</p>
	 <p>For overhead installations support the anchor rod with wedges. (e.g. fischer centering wedges) until the the mortar begins to cure</p>	 <p>For push through installation fill the annular gap with mortar</p>
11	 <p>Wait for the specified curing time t_{cure} see Table B5</p>	<div data-bbox="773 1006 853 1192">12</div>  <p>Mounting the fixture $T_{\text{inst,max}}$ see Table B2</p>

fischer injection system FIS EB


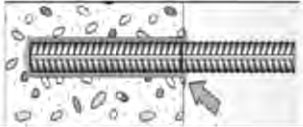

Intended use
Installation instructions part 3

Annex B 8

Appendix 13 / 24

Installation instructions part 4

Installation reinforcing bars

10		Only use clean and oil-free reinforcing bars. Mark the setting depth. Turn while using force to push the reinforcing bar into the filled hole up to the setting depth mark
		When the setting depth mark is reached, excess mortar must be emerged from the mouth of the drill hole. If not, pull out the anchor element immediately and reinject mortar
11		Wait for the specified curing time t_{cure} see Table B5

fischer injection system FIS EB

Intended use
Installation instructions part 4

Annex B 9

Appendix 14 / 24

Table C1: Characteristic values for the steel bearing capacity under tensile / shear load of fischer anchor rods and standard threaded rods

Size				M8	M10	M12	M14	M16	M20	M22	M24	M27	M30
Bearing capacity under tensile load, steel failure													
Charact.bearing capacity $N_{Rk,s}$	Steel zinc plated	5.8	[kN]	19	29	43	58	79	123	152	177	230	281
		8.8		29	47	68	92	126	196	243	282	368	449
	Stainless steel A4	50		19	29	43	58	79	123	152	177	230	281
		70		26	41	59	81	110	172	212	247	322	393
		80		30	47	68	92	126	196	243	282	368	449
Partial safety factors ¹⁾													
Partial safety factor $\gamma_{Ms,N}$	Steel zinc plated	5.8	[-]	1,50									
		8.8		1,50									
	Stainless steel A4	50		2,86									
		70		1,87									
		80		1,60									
Bearing capacity under shear load, steel failure													
without lever arm													
Charact. bearing capacity $V_{Rk,s}$	Steel zinc plated	5.8	[kN]	9	15	21	29	39	61	76	89	115	141
		8.8		15	23	34	46	63	98	122	141	184	225
	Stainless steel A4	50		9	15	21	29	39	61	76	89	115	141
		70		13	20	30	40	55	86	107	124	161	197
		80		15	23	34	46	63	98	122	141	184	225
Duktilitätsfaktor gemäß CEN/TS 1992-4-5:2009 Abschnitt 6.3.2.1		k_2	[-]	1,0									
with lever arm													
Charact. bending moment $M^0_{Rk,s}$	Steel zinc plated	5.8	[Nm]	19	37	65	104	166	324	447	560	833	1123
		8.8		30	60	105	167	266	519	716	896	1333	1797
	Stainless steel A4	50		19	37	65	104	166	324	447	560	833	1123
		70		26	52	92	146	232	454	626	784	1167	1573
		80		30	60	105	167	266	519	716	896	1333	1797
Partial safety factors ¹⁾													
Partial safety factor $\gamma_{Ms,V}$	Steel zinc plated	5.8	[-]	1,25									
		8.8		1,25									
	Stainless steel A4	50		2,38									
		70		1,56									
		80		1,33									

¹⁾ In absence of other national regulations

fischer injection system FIS EB

Performances

Characteristic steel bearing capacity of fischer anchor rods and standard threaded rods

Annex C 1

Appendix 15 / 24

Table C2: Characteristic values for the **steel bearing capacity** under tensile / shear load of **reinforcing bars**

Nominal diameter of the bar		ϕ	8	10	12	14	16	18	20	22	24	25	26	28	30	32	34	36	40
Bearing capacity under tensile load, steel failure																			
Characteristic bearing capacity	$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}^{1)}$																
Bearing capacity under shear load, steel failure																			
without lever arm																			
Characteristic bearing capacity	$V_{Rk,s}$	[kN]	$0,5 \cdot A_s \cdot f_{uk}^{1)}$																
Ductility factor acc. to CEN/TS 1992-4-5:2009 Section 6.3.2.1	k_2	[-]	0,8																
with lever arm																			
Characteristic bending moment	$M_{Rk,s}^0$	[Nm]	$1,2 \cdot W_{el} \cdot f_{uk}^{1)}$																

¹⁾ f_{uk} or f_{yk} respectively must be taken from the specifications of the reinforcing bar

fischer injection system FIS EB

Performances

Characteristic steel bearing capacity of reinforcing bars

Annex C 2

Appendix 16 / 24

Table C3: General design factors for the bearing capacity under tensile / shear load; **uncracked or cracked concrete**

Size			All Sizes																			
Bearing capacity under tensile load																						
Factors acc. to CEN/TS 1992-4:2009 Section 6.2.2.3																						
Uncracked concrete		k_{ucr}	[-]	10,1																		
Cracked concrete		k_{cr}		7,2																		
Factors for the compressive strength of concrete > C20/25																						
Increasing factor for τ_{Rk}	C25/30		Ψ_c	[-]	1,02																	
	C30/37				1,04																	
	C35/45				1,06																	
	C40/50				1,07																	
	C45/55				1,08																	
	C50/60				1,09																	
Splitting failure																						
Edge distance	$h / h_{ef} \geq 2,0$		$c_{cr,sp}$	[mm]	1,0 h_{ef}																	
	$2,0 > h / h_{ef} > 1,3$				4,6 h_{ef} - 1,8 h																	
	$h / h_{ef} \leq 1,3$				2,26 h_{ef}																	
Spacing		$s_{cr,sp}$			2 $c_{cr,sp}$																	
Bearing capacity under shear load																						
Installation safety factors																						
All installation conditions		$\gamma_2 = \gamma_{inst}$	[-]	1,0																		
Concrete pry-out failure																						
Factor k acc. to TR029 Section 5.2.3.3 resp. k_3 acc. to CEN/TS 1992-4-5:2009 Section 6.3.3		$k_{(3)}$	[-]	2,0																		
Concrete edge failure																						
The value of h_{ef} (= l_f) under shear load			[mm]	min (h_{ef} ; 8d)																		
Calculation diameters																						
Size				M8	M10	M12	M14	M16	M20	M22	M24	M27	M30									
fischer anchor rods and standard threaded rods		d	[mm]	8	10	12	14	16	20	22	24	27	30									
Nominal diameter of the bar				ϕ	8	10	12	14	16	18	20	22	24	25	26	28	30	32	34	36	40	
Reinforcing bar				d	[mm]	8	10	12	14	16	18	20	22	24	25	26	28	30	32	34	36	40

fischer injection system FIS EB

Performances

General design factors relating to the characteristic bearing capacity under tensile / shear load

Annex C 3

Appendix 17 / 24

Table C4: Characteristic values of **resistance** for **fischer anchor rods** and **standard threaded rods** under **tensile load** in hammer or diamond drilled holes; **uncracked or cracked concrete**

Size			M8	M10	M12	M14	M16	M20	M22	M24	M27	M30
Combined pullout and concrete cone failure												
Calculation diameter	d	[mm]	8	10	12	14	16	20	22	24	27	30
Uncracked concrete												
Characteristic bond resistance in uncracked concrete C20/25												
Hammer-drilling with standard drill bit or hollow drill bit (dry and wet concrete)												
	$\tau_{Rk,ucr}$	[N/mm ²]	11	10	10	9	9	8	8	8	7,5	7,5
Hammer-drilling with standard drill bit or hollow drill bit (flooded hole)												
	$\tau_{Rk,ucr}$	[N/mm ²]	11	10	10	9	8	7,5	7	7	6	6
Diamond-drilling (dry and wet concrete)												
	$\tau_{Rk,ucr}$	[N/mm ²]	11	10	8	7,5	7,5	7	6	6	5,5	5,5
Diamond-drilling (flooded hole)												
	$\tau_{Rk,ucr}$	[N/mm ²]	11	10	8	7,5	7,5	7	6	6	5,5	5,5
Installation safety factors												
Dry and wet concrete	$\gamma_2 = \gamma_{inst}$	[-]	1,0						1,2			
Flooded hole			1,4									
Cracked concrete												
Characteristic bond resistance in cracked concrete C20/25												
Hammer-drilling with standard drill bit or hollow drill bit and diamond-drilling (dry and wet concrete)												
	$\tau_{Rk,cr}$	[N/mm ²]	5	5	5	5	4	4	5	5	5	5
Hammer-drilling with standard drill bit or hollow drill bit and diamond-drilling (flooded hole)												
	$\tau_{Rk,cr}$	[N/mm ²]	4	5	5	5	4	4	4	4	4	4
Installation safety factors												
Dry and wet concrete	$\gamma_2 = \gamma_{inst}$	[-]	1,0						1,2			
Flooded hole			1,2						1,4			

fischer injection system FIS EB

Performances

Characteristic values for static or quasi-static action under tensile load for fischer anchor rods and standard threaded rods (uncracked or cracked concrete)

Annex C 4

Appendix 18 / 24

Table C5: Characteristic values of resistance under tensile load for reinforcing bars in hammer or diamond drilled holes; uncracked or cracked concrete

Nominal diameter of the bar		ϕ	8	10	12	14	16	18	20	22	24	25	26	28	30	32	34	36	40	
Combined pullout and concrete cone failure																				
Calculation diameter		d	[mm]	8	10	12	14	16	18	20	22	24	25	26	28	30	32	34	36	40
Uncracked concrete																				
Characteristic bond resistance in uncracked concrete C20/25																				
Hammer-drilling with standard drill bit or hollow drill bit (dry and wet concrete)																				
$\tau_{RK,ucr}$		[N/mm ²]	11	10	10	9	9	9	8	8	8	8	7,5	7,5	7,5	7,5	7,5	7,5	7	
Hammer-drilling with standard drill bit or hollow drill bit (flooded hole)																				
$\tau_{RK,ucr}$		[N/mm ²]	11	10	9	8	7,5	8	7,5	7	7	6	6	6	6	5,5	5,5	5,5	5,5	
Diamond-drilling (dry and wet concrete as well as flooded hole)																				
$\tau_{RK,ucr}$		[N/mm ²]	11	10	8	7,5	7,5	7	7	6	6	6	5,5	5,5	5,5	5,5	5	5	5	
Installation safety factors																				
Dry and wet concrete		$\gamma_2 = \gamma_{inst}$	[-]	1,0							1,2									
Flooded hole				1,4																
Cracked concrete																				
Characteristic bond resistance in cracked concrete C20/25																				
Hammer-drilling with standard drill bit or hollow drill bit and diamond-drilling (dry and wet concrete)																				
$\tau_{RK,cr}$		[N/mm ²]	5	5	5	5	4	4	4	5	5	5	5	5	5	3,5	3,5	3,5	3,5	
Hammer-drilling with standard drill bit or hollow drill bit and diamond-drilling (flooded hole)																				
$\tau_{RK,cr}$		[N/mm ²]	4	4,5	4,5	4	4	4	4	4	4	4	4	4	4	3,5	3,5	3,5	3,5	
Installation safety factors																				
Dry and wet concrete		$\gamma_2 = \gamma_{inst}$	[-]	1,0							1,2									
Flooded hole				1,2							1,4									

fischer injection system FIS EB

Performances

Characteristic values for static or quasi-static action under tensile load for reinforcing bars (uncracked or cracked concrete)

Annex C 5

Appendix 19 / 24

Table C6: Displacements for anchor rods

Size		M8	M10	M12	M14	M16	M20	M22	M24	M27	M30
Displacement-Factors for tensile load ¹⁾											
Uncracked or cracked concrete											
δ_{N0} -Factor	[mm/(N/mm ²)]	0,07	0,08	0,09	0,09	0,10	0,11	0,11	0,12	0,12	0,13
$\delta_{N\infty}$ -Factor		0,11	0,12	0,13	0,14	0,15	0,16	0,17	0,18	0,19	0,19
Displacement-Factors for shear load ²⁾											
Uncracked or cracked concrete											
δ_{V0} -Factor	[mm/kN]	0,18	0,15	0,12	0,10	0,09	0,07	0,07	0,06	0,05	0,05
$\delta_{V\infty}$ -Factor		0,27	0,22	0,18	0,16	0,14	0,11	0,10	0,09	0,08	0,07

1) Calculation of effective displacement:

$$\delta_{N0} = \delta_{N0\text{-Factor}} \cdot \tau_{Ed}$$

$$\delta_{N\infty} = \delta_{N\infty\text{-Factor}} \cdot \tau_{Ed}$$

(τ_{Ed} : Design value of the applied tensile stress)

2) Calculation of effective displacement:

$$\delta_{V0} = \delta_{V0\text{-Factor}} \cdot V_{Ed}$$

$$\delta_{V\infty} = \delta_{V\infty\text{-Factor}} \cdot V_{Ed}$$

(V_{Ed} : Design value of the applied shear force)

Table C7: Displacements for reinforcing bars

Nominal diameter of the bar	ϕ	8	10	12	14	16	18	20	22	24	25	26	28	30	32	34	36	40
Displacement-Factors for tensile load ¹⁾																		
Uncracked or cracked concrete																		
δ_{N0} -Factor	[mm/(N/mm ²)]	0,07	0,08	0,09	0,09	0,10	0,10	0,11	0,11	0,12	0,12	0,12	0,13	0,13	0,13	0,14	0,14	0,15
$\delta_{N\infty}$ -Factor		0,11	0,12	0,13	0,14	0,15	0,16	0,16	0,17	0,18	0,18	0,18	0,19	0,19	0,20	0,20	0,21	0,22
Displacement-Factors for shear load ²⁾																		
Uncracked or cracked concrete																		
δ_{V0} -Factor	[mm/kN]	0,18	0,15	0,12	0,10	0,09	0,08	0,07	0,07	0,06	0,06	0,06	0,05	0,05	0,05	0,04	0,04	0,04
$\delta_{V\infty}$ -Factor		0,27	0,22	0,18	0,16	0,14	0,12	0,11	0,10	0,09	0,09	0,08	0,08	0,07	0,07	0,06	0,06	0,05

1) Calculation of effective displacement:

$$\delta_{N0} = \delta_{N0\text{-Factor}} \cdot \tau_{Ed}$$

$$\delta_{N\infty} = \delta_{N\infty\text{-Factor}} \cdot \tau_{Ed}$$

(τ_{Ed} : Design value of the applied tensile stress)

2) Calculation of effective displacement:

$$\delta_{V0} = \delta_{V0\text{-Factor}} \cdot V_{Ed}$$

$$\delta_{V\infty} = \delta_{V\infty\text{-Factor}} \cdot V_{Ed}$$

(V_{Ed} : Design value of the applied shear force)

fischer injection system FIS EB

Performances

Displacements for anchor rods and reinforcing bars

Annex C 6

Appendix 20 / 24

Table C8: Characteristic values for the steel bearing capacity of fischer anchor rods and standard threaded rods under seismic action performance category C1 or C2

Size				M10	M12	M14	M16	M20	M22	M24	M27	M30			
Bearing capacity under tensile load, steel failure ¹⁾															
fischer anchor rods and standard threaded rods, performance category C1															
Charact.bearing capacity $N_{Rk,s,C1}$	Steel zinc plated	Property class	5.8	[kN]	29	43	58	79	123	152	177	230	281		
			8.8		47	68	92	126	196	243	282	368	449		
	Stainless steel A4		50		29	43	58	79	123	152	177	230	281		
			70		41	59	81	110	172	212	247	322	393		
			80		47	68	92	126	196	243	282	368	449		
	fischer anchor rods and standard threaded rods, performance category C2														
	Charact.bearing capacity $N_{Rk,s,C2}$		Steel zinc plated		Property class	5.8	[kN]	---	39	---	72	108	---	177	---
8.8		---		61		---		116	173	---	282	---	---		
Stainless steel A4		50	---	39		---		72	108	---	177	---	---		
		70	---	53		---		101	152	---	247	---	---		
		80	---	61		---		116	173	---	282	---	---		
Bearing capacity under shear load, steel failure without lever arm ¹⁾															
fischer anchor rods, performance category C1															
Charact.bearing capacity $V_{Rk,s,C1}$	Steel zinc plated	Property class	5.8	[kN]	15	21	29	39	61	76	89	115	141		
			8.8		23	34	46	63	98	122	141	184	225		
	Stainless steel A4		50		15	21	29	39	61	76	89	115	141		
			70		20	30	40	55	86	107	124	161	197		
			80		23	34	46	63	98	122	141	184	225		
	Standard threaded rods, performance category C1														
	Charact.bearing capacity $V_{Rk,s,C1}$		Steel zinc plated		Property class	5.8	[kN]	11	15	20	27	43	53	62	81
8.8		16		24		32		44	69	85	99	129	158		
Stainless steel A4		50	11	15		20		27	43	53	62	81	99		
		70	14	21		28		39	60	75	87	113	138		
		80	16	24		32		44	69	85	99	129	158		
fischer anchor rods and standard threaded rods, performance category C2															
Charact.bearing capacity $V_{Rk,s,C2}$		Steel zinc plated	Property class	5.8		[kN]		---	14	---	27	43	---	62	---
	8.8			---	22		---	44	69	---	99	---	---		
	Stainless steel A4	50		---	14		---	27	43	---	62	---	---		
		70		---	20		---	39	60	---	87	---	---		
		80		---	22		---	44	69	---	99	---	---		

¹⁾ Partial safety factors for performance category C1 or C2 see Table C10, for fischer anchor rods FIS A / RGM the factor for steel ductility is 1,0

fischer injection system FIS EB

Performances

Characteristic steel bearing capacity of fischer anchor rods and standard threaded rods under seismic action (performance category C1 or C2)

Annex C 7

Appendix 21 / 24

Table C9: Characteristic values for the steel bearing capacity of reinforcing bars (B500B) under seismic action performance category C1

Nominal diameter of the bar ϕ		10	12	14	16	18	20	22	24	25	26	28	30	32
Bearing capacity under tensile load, steel failure¹⁾														
Reinforcing bar B500B acc. to DIN 488-2:2009-08, performance category C1														
Characteristic bearing capacity	$N_{Rk,s,C1}$	[kN]	44	63	85	111	140	173	209	249	270	292	339	443
Bearing capacity under shear load, steel failure without lever arm¹⁾														
Reinforcing bar B500B acc. to DIN 488-2:2009-08, performance category C1														
Characteristic bearing capacity	$V_{Rk,s,C1}$	[kN]	15	22	30	39	49	61	74	88	95	102	119	155

¹⁾ Partial safety factors for performance category C1 see Table C10

Table C10: Partial safety factors of fischer anchor rods, standard threaded rods and reinforcing bars (B500B) under seismic action performance category C1 or C2

Size				M10	M12	M14	M16	M20	M22	M24	M27	M30				
Nominal diameter of the bar ϕ				10	12	14	16	18	20	22	24	25	26	28	30	32
Bearing capacity under tensile load, steel failure ¹⁾																
Partial safety factor $\gamma_{Ms,N}$	Steel zinc plated	Property class	5.8	[-]	1,50											
			8.8		1,50											
	Stainless steel A4		50		2,86											
			70		1,87											
			80		1,60											
	Reinforcing bar ²⁾		B500B		1,40											
Bearing capacity under shear load, steel failure ¹⁾																
Partial safety factor $\gamma_{Ms,V}$	Steel zinc plated	Property class	5.8	[-]	1,25											
			8.8		1,25											
	Stainless steel A4		50		2,38											
			70		1,56											
			80		1,33											
	Reinforcing bar ²⁾		B500B		1,50											

¹⁾ In absence of other national regulations

²⁾ Reinforcing bars only seismic action category C1

fischer injection system FIS EB

Performances

Characteristic steel bearing capacity of reinforcing bars under seismic action (performance category C1); partial safety factors (performance category C1 or C2)

Annex C 8

Appendix 22 / 24

Table C11: Characteristic values of **resistance** for **fischer anchor rods** and **standard threaded rods** in hammer drilled holes under seismic action performance category **C1**

Size		M10	M12	M14	M16	M20	M22	M24	M27	M30
Characteristic bond resistance, combined pullout and concrete cone failure										
Hammer-drilling with standard drill bit or hollow drill bit (dry and wet concrete)										
$\tau_{Rk,C1}$	[N/mm²]	4,9	4,9	4,6	4,0	4,0	4,6	4,6	4,6	4,6
Hammer-drilling with standard drill bit or hollow drill bit (flooded hole)										
$\tau_{Rk,C1}$	[N/mm²]	4,7	4,7	4,5	4,0	4,0	4,0	4,0	4,0	4,0
Installation safety factors										
Bearing capacity under tensile load										
Dry and wet concrete	$\gamma_2 = \gamma_{inst}$	[-]	1,0				1,2			
Flooded hole			1,2				1,4			
Bearing capacity under shear load										
All installation conditions	$\gamma_2 = \gamma_{inst}$	[-]	1,0							

Table C12: Characteristic values of **resistance** for **reinforcing bars** in hammer drilled holes under seismic action performance category **C1**

Nominal diameter of the bar	ϕ	10	12	14	16	18	20	22	24	25	26	28	30	32
Characteristic bond resistance, combined pullout and concrete cone failure														
Hammer-drilling with standard drill bit or hollow drill bit (dry and wet concrete)														
$\tau_{Rk,C1}$	[N/mm ²]	4,9	4,9	4,6	4,0	4,0	4,0	4,6	4,6	4,6	4,6	4,6	4,6	3,4
Hammer-drilling with standard drill bit or hollow drill bit (flooded hole)														
$\tau_{Rk,C1}$	[N/mm ²]	4,7	4,7	4,1	4,1	4,0	4,0	4,0	4,0	4,0	4,0	4,0	4,0	3,4
Installation safety factors														
Bearing capacity under tensile load														
Dry and wet concrete	$\gamma_2 = \gamma_{inst}$	[-]	1,0						1,2					
Flooded hole			1,2						1,4					
Bearing capacity under shear load														
All installation conditions	$\gamma_2 = \gamma_{inst}$	[-]	1,0											

fischer injection system FIS EB

Performances

Characteristic values under seismic action (performance category C1) for fischer anchor rods, standard threaded rods and reinforcing bars

Annex C 9

Appendix 23 / 24

Table C13: Characteristic values of **resistance** for **fischer anchor rods** and **standard threaded rods** in hammer drilled holes under seismic action performance category **C2**

Size		M12	M16	M20	M24
Characteristic bond resistance, combined pullout and concrete cone failure					
Hammer-drilling with standard drill bit or hollow drill bit (dry and wet concrete)					
$\tau_{Rk,C2}$	[N/mm²]	1,5	2,5	1,3	1,7
Hammer-drilling with standard drill bit or hollow drill bit (flooded hole)					
$\tau_{Rk,C2}$	[N/mm²]	1,6	2,5	1,3	1,4
Installation safety factors					
Bearing capacity under tensile load					
Dry and wet concrete	$\gamma_2 = \gamma_{inst}$	[-]	1,0		1,2
Flooded hole			1,2		1,4
Bearing capacity under shear load					
All installation conditions	$\gamma_2 = \gamma_{inst}$	[-]	1,0		
Displacement-Factors for tensile load ¹⁾					
$\delta_{N,(DLS)}\text{-Factor}$	[mm/(N/mm²)]	0,09	0,10	0,11	0,12
$\delta_{N,(ULS)}\text{-Factor}$		0,15	0,17	0,17	0,18
Displacement-Factors for shear load ²⁾					
$\delta_{V,(DLS)}\text{-Factor}$	[mm/kN]	0,18	0,10	0,07	0,06
$\delta_{V,(ULS)}\text{-Factor}$		0,25	0,14	0,11	0,09

1) Calculation of effective displacement:

$$\delta_{N,(DLS)} = \delta_{N,(DLS)\text{-Factor}} \cdot \tau_{Ed}$$

$$\delta_{N,(ULS)} = \delta_{N,(ULS)\text{-Factor}} \cdot \tau_{Ed}$$

(τ_{Ed} : Design value of the applied tensile stress)

2) Calculation of effective displacement:

$$\delta_{V,(DLS)} = \delta_{V,(DLS)\text{-Factor}} \cdot V_{Ed}$$

$$\delta_{V,(ULS)} = \delta_{V,(ULS)\text{-Factor}} \cdot V_{Ed}$$

(V_{Ed} : Design value of the applied shear force)

fischer injection system FIS EB

Performances

Characteristic values under seismic action (performance category C2) for fischer anchor rods and standard threaded rods

Annex C 10

Appendix 24 / 24